

Halar®



SOLVAY

asking more from chemistry®




Halar® XPH-800

Thermal Aging Study

**SPECIALTY
POLYMERS**

Thermal Aging Study of Halar® XPH-800

Halar® ECTFE is a partially fluorinated, semi-crystalline, melt-processable thermoplastic manufactured by Solvay Specialty Polymers at its ISO-certified plant in Orange, Texas. ECTFE is produced via the copolymerization of ethylene and chlorotrifluoroethylene monomers and has the following chemical formula:

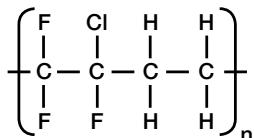


1:1 alternating copolymer

This chemical structure gives Halar® ECTFE a unique combination of properties including excellent chemical resistance and a high thermal rating, thanks to the strength of its carbon-fluorine chemical bonds. It also has excellent mechanical properties as a result of the strong inter-chain interactions of hydrogen bonding.

Halar® XPH-800 delivers enhanced stress cracking performance due to chain structure modifications of the ECTFE polymer.

Tensile properties of Halar® XPH-800 thermally aged at 189 °C (372 °F)

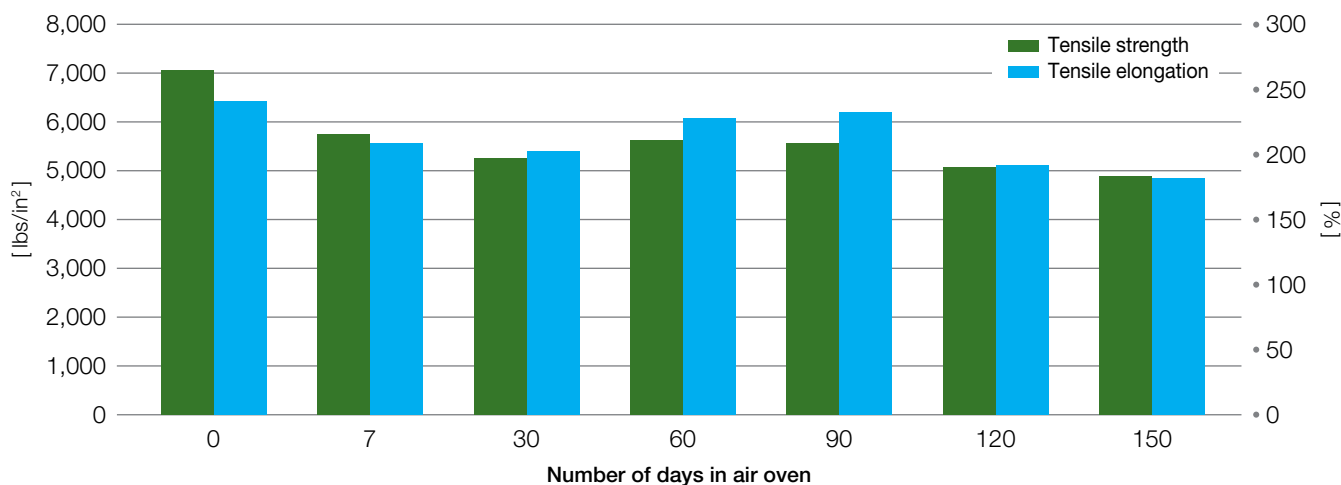

Tensile strength & elongation of thermally aged Halar® XPH-800*

Units	Number of Days in Air Oven						
	0	7	30	60	90	120	150
Tensile strength at 23 °C (73 °F)	7,033						
Tensile strength after aging at 189 °C (372 °F)		5,730	5,243	5,622	5,568	5,049	4,874
Tensile strength after aging at 200 °C (392 °F)		5,077	5,201	3,759	3,938	3,575	3,780
Elongation at 23 °C (73 °F)	267						
Elongation after aging at 189 °C (372 °F)		209	201	227	233	191	181
Elongation after aging at 200 °C (392 °F)		158	150	4	4	5	5

* Cable insulation was tested for the dry temperature rating of new materials (long-term aging test) according to UL 2556 and the material received a 180 °C (356 °F) rating.

www.solvay.com

SpecialtyPolymers.EMEA@solvay.com | Europe, Middle East and Africa

SpecialtyPolymers.Americas@solvay.com | Americas

SpecialtyPolymers.Asia@solvay.com | Asia Pacific



SOLVAY

asking more from chemistry®

Safety Data Sheets (SDS) are available by emailing us or contacting your sales representative. Always consult the appropriate SDS before using any of our products. Neither Solvay Specialty Polymers nor any of its affiliates makes any warranty, express or implied, including merchantability or fitness for use, or accepts any liability in connection with this product, related information or its use. Some applications of which Solvay's products may be proposed to be used are regulated or restricted by applicable laws and regulations or by national or international standards and in some cases by Solvay's recommendation, including applications of food/feed, water treatment, medical, pharmaceuticals, and personal care. Only products designated as part of the Solviva® family of biomaterials may be considered as candidates for use in implantable medical devices. The user alone must finally determine suitability of any information or products for any contemplated use in compliance with applicable law, the manner of use and whether any patents are infringed. The information and the products are for use by technically skilled persons at their own discretion and risk and does not relate to the use of this product in combination with any other substance or any other process. This is not a license under any patent or other proprietary right. All trademarks and registered trademarks are property of the companies that comprise Solvay Group or their respective owners.

© 2014 Solvay Specialty Polymers. All rights reserved. D06/2014 | Version 1.0